

# A molecular dynamics study on the formation of metal-containing fullerene

Yasutaka Yamaguchi<sup>\*1</sup> and Shigeo Maruyama<sup>\*2</sup>  
Computational Science Laboratory

It is experimentally proved that transition metals such as La, Y or Sc can be trapped inside of fullerene cage, called metal-containing fullerenes. The growth mechanism of metal-containing fullerenes is currently a crucial issue in many fields. In this paper, the growth process of metal-containing fullerenes is studied by using the molecular dynamics method which is similar to our simulations of perfect  $C_{60}$  and  $C_{70}$  formation.<sup>1,2)</sup> In order to model the potential function between carbon and metal atoms appropriate for the MD simulation, the binding energy and charge state of various forms of small clusters  $ScC_n$  ( $n = 1-3$ ) were calculated with the density functional theory based on the Becke<sup>3)</sup> three-parameter(B3) exchange functional with the Lee-Yang-Parr<sup>4)</sup>(LYP) correlation. A multi-body potential function was constructed as a function of coordinate number of a scandium atom. Here, the Coulomb term and the Morse-type term were separately described considering the large charge transfer from a scandium atom to carbon atoms.

The clustering process starting from 500 isolated carbon atoms and 5 scandium atoms in a 34.2 nm cubic cell was simulated under the controlled temperature condition, where the translational, rotational and vibrational temperatures of each cluster were kept nearly equilibrium at  $T_c = 3000$  K. Figure 1 shows the growth process of a  $Sc@C_{92}$  cluster obtained at 3000 ps. The vertical position and horizontal length denote the size and the duration of existence of clusters, respectively. When the cluster was smaller than  $Sc+C_6$ , a fan-type structure was reproduced around the scandium atom. When it grew to about  $Sc+C_8$ , the scandium atom positioned out of the monocyclic carbon ring. Then, the scandium atom approached to the center of the monocyclic ring when the cluster grew as large as  $Sc+C_{13}$ . The host monocyclic ring changed to a bi-cyclic ring with keeping the scandium atom in the same plane around  $C_{16}$ . When the host carbon cluster grew as large as  $C_{19}$ , it annealed to a graphitic sheet and the scandium atom was driven out of the plane. Here, the Coulomb force induced curvature to the sheet, and the cluster grew larger until about  $Sc+C_{27}$  keeping the open-

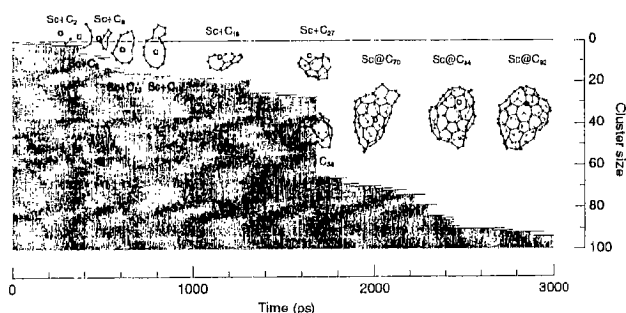


Fig. 1. Growth process of a scandium-containing fullerene.

cap structure. Then, in this case, a collision with a large cluster of  $C_{38}$  prevented gradual growth and resulted in the formation of  $Sc@C_{66}$  where the scandium atom was almost enclosed in the carbon cage. The number of carbon atoms was not enough to form a complete closed cage until around  $C_{84}$ , when a hollow caged structure similar to fullerene cage first appeared. Considering the difference of time and temperature scale between the real phenomena and simulation, these hollow caged structures could have sufficient collision free annealing interval to form more sophisticated structures like experimentally isolated metal-containing fullerenes. Compared to the formation process of empty fullerenes in our previous simulations,<sup>1,2)</sup> the main difference is the open-cap structure around  $C_{20-30}$ , and that seems to affect the low yield of metal-containing fullerenes.

## References

- 1) Y. Yamaguchi and S. Maruyama: Chem. Phys. Lett. **286**, 336 (1998).
- 2) S. Maruyama and Y. Yamaguchi: Chem. Phys. Lett. **286**, 343 (1998).
- 3) A. D. Becke: J. Chem. Phys. **98**, 5648 (1993).
- 4) C. Lee et al.: Phys. Rev. B **37**, 785 (1988).

<sup>\*1</sup> University of Tokyo, yaya@photon.t.u-tokyo.ac.jp

<sup>\*2</sup> Permanent address: University of Tokyo